

Polarization dependence of coherent phonon generation and detection in highly-aligned single-walled carbon nanotubes

L. G. Booshehri,^{1,2} C. L. Pint,^{2,3,4} G. D. Sanders,⁵ L. Ren,^{1,2} C. Sun,^{1,2} E. H. Házó,^{1,2} J.-H. Kim,⁶ K.-J. Yee,⁶ Y.-S. Lim,⁷ R. H. Hauge,^{2,4} C. J. Stanton,⁵ and J. Kono^{1,2,3,*}

¹*Department of Electrical and Computer Engineering, Rice University, Houston, Texas 77005, USA*

²*The Richard E. Smalley Institute for Nanoscale Science and Technology, Rice University, Houston, Texas 77005, USA*

³*Department of Physics and Astronomy, Rice University, Houston, Texas 77005, USA*

⁴*Department of Chemistry, Rice University, Houston, Texas 77005, USA*

⁵*Department of Physics, University of Florida, Box 118440, Gainesville, Florida 32611-8440, USA*

⁶*Department of Physics, Chungnam National University, Daejeon, 305-764, Republic of Korea*

⁷*Department of Applied Physics, Konkuk University, Chungju, Chungbuk, 380-701, Republic of Korea*

(Received 15 July 2010; revised manuscript received 20 March 2011; published 5 May 2011)

We have investigated the polarization dependence of the generation and detection of radial breathing mode (RBM) coherent phonons (CPs) in highly-aligned single-walled carbon nanotubes. Using polarization-dependent pump-probe differential-transmission spectroscopy, we measured RBM CPs as a function of angle for two different geometries. In Type I geometry, the pump and probe polarizations were fixed, and the sample orientation was rotated whereas, in Type II geometry, the probe polarization and sample orientation were fixed, and the pump polarization was rotated. In both geometries, we observed an almost complete quenching of the RBM CPs when the pump polarization was perpendicular to the nanotubes. For both Type I and II geometries, we have developed a microscopic theoretical model to simulate CP generation and detection as a function of polarization angle and found that the CP signal decreases as the angle goes from 0° (parallel to the tube) to 90° (perpendicular to the tube). We compare theory with experiment in detail for RBM CPs created by pumping at the E_{44} optical transition in an ensemble of single-walled carbon nanotubes with a diameter distribution centered around 3 nm, taking into account realistic band structure and imperfect nanotube alignment in the sample. We theoretically determined a $\cos^8(\theta)$ dependence for Type I CP spectroscopy experiments and a $\cos^4(\phi)$ polarization dependence for Type II CP spectroscopy experiments and, after including misalignment effects to our fitting, we determined the nematic order parameter of our sample to be 0.81.

DOI: [10.1103/PhysRevB.83.195411](https://doi.org/10.1103/PhysRevB.83.195411)

PACS number(s): 78.67.Ch, 73.22.-f

I. INTRODUCTION

The one-dimensional (1D) nature of single-walled carbon nanotubes (SWNTs) is attractive from both fundamental and applied points of view, where the 1D confinement of electrons and phonons results in unique anisotropic electric, magnetic, mechanical, and optical properties.^{1,2} Individualized SWNTs, both in single-tube and ensemble samples, have shown anisotropy in polarized Raman scattering experiments and optical absorption measurements where maximum signals result when the nanotube axis is aligned parallel to the polarization of the incident light.³⁻⁸ Additionally, due to strong anisotropic magnetic susceptibilities, both semiconducting and metallic SWNTs align well within an external magnetic field, and with the added properties of the Aharonov-Bohm effect, the electronic band structure of SWNTs respond anisotropically with the strength of a tube-threading magnetic flux.⁹⁻¹⁶ Such optical and magnetic anisotropy is also expected with bulk samples, but detailed measurements showing extreme anisotropy have been lacking.¹⁷

Here we investigate anisotropic optical and vibrational properties of a bulk film of highly-aligned SWNTs using polarization-dependent coherent phonon (CP) spectroscopy. CP spectroscopy is an ultrafast pump-probe technique that complements CW Raman scattering spectroscopy and, although both techniques provide information about electron-

phonon coupling, CP spectroscopy avoids the common disadvantages of Raman scattering spectroscopy that include detection of Rayleigh scattering and photoluminescence and the broadening and blending of peak features.¹⁸ Such advantages are useful when investigating SWNTs, where a large majority of samples include ensembles dispersed in various environments with optical properties that are obscured by the collection of varying species of nanotubes in the ensemble.

The advantages of CP spectroscopy are also seen in comparison to time-resolved vibrational spectroscopy. Additional ultrafast techniques have been employed to investigate electron-phonon coupling and, in particular, time-resolved anti-Stokes Raman scattering measurements have been used to determine the population lifetimes of G-band phonons in SWNTs.^{19,20} However, the information obtained from such time-resolved measurements is limited to population lifetimes of phonons and do not provide the additional phase information and dephasing times that are accessible with CP spectroscopy. Recent CP studies on SWNTs have produced direct observation of CP oscillations of both the radial breathing mode (RBM) and G-band phonons, in addition to their phase information and dephasing times.^{18,21-26} Furthermore, when pulse-shaping techniques are combined with CP spectroscopy, predesigned trains of femtosecond pulses selectively excite RBM CPs of a specific chirality, avoiding inhomogeneous broadening from the ensemble.²⁵ However, it is important to note that previous

CP studies investigated randomly aligned SWNT samples and, because the quasi-1D nature of SWNTs leads to optical anisotropy that is dominant in the polarization dependence of photoluminescence (PL), absorption, and Raman scattering, CP studies on aligned SWNTs are necessary.

Below, we present results of a detailed experimental and theoretical study of CPs in highly-aligned SWNT thin films and found a very strong polarization anisotropy of the RBM as a function of angle. In particular, we observed an almost complete quenching of the RBM when the optical polarization is perpendicular to the tubes. We have developed a theoretical model to understand this extreme anisotropy, including band structure, interband optical transition elements, ultrafast carrier and phonon dynamics, and imperfect nanotube alignment in the sample. Fitting our results to theory, we also calculated the nematic order parameter $S^{8,15-17}$ (i.e., the degree of SWNT alignment in the sample).

II. SAMPLES AND EXPERIMENTAL METHODS

We investigated CPs through degenerate pump-probe spectroscopy measurements on highly-aligned SWNT thin films transferred onto sapphire substrates. Patterned, vertically aligned SWNT arrays were first grown using a modified supergrowth water-assisted chemical vapor deposition (CVD) technique on SiO_2 substrates coated with catalyst pads composed of 10 and 0.5 nm of Al_2O_3 and Fe, respectively. Following growth, the patterned SWNT arrays were subjected to a 3 minute $\text{H}_2/\text{H}_2\text{O}$ gas-phase etch at 750 °C to remove metal-carbon bonds and facilitate dry transfer of the patterns to a sapphire substrate. This converts the vertically aligned SWNT patterns to horizontally aligned SWNTs, with a length and density defined by the growth duration and features of the mask used for photolithography, respectively.²⁷ For experiments reported here, the SWNT layer is 2 μm thick, with SWNTs having ultralong lengths of $\sim 50 \mu\text{m}$ and separated by a pitch of $\sim 50 \mu\text{m}$. The real thickness is less than 2 μm as 2 μm was the thickness of the as-grown line whereas the laid-over line could be as much as one tenth of that thickness due to compression from the less dense as-grown line of SWNTs. The SWNTs formed using this technique are highly aligned and have a diameter distribution ranging between 1 to 5 nm, centered around 3 nm.^{17,28}

Figure 1(a) shows polarization-dependent absorption spectra of a typical aligned sample in the visible to near-infrared range, while Fig. 1(b) shows absorption spectra in the far-infrared or terahertz (THz) range. The polarization anisotropy is obvious in both (a) and (b) but extreme in the THz regime (b), as there is virtually zero absorption when the sample is perpendicular to the THz polarization.¹⁷ Therefore, with such an aligned sample, our polarization measurements can be extended to include the sample as an additional rotation parameter, compared to our earlier study of CP polarization dependence in randomly aligned SWNTs.²³

Using a mode-locked Ti:Sapphire laser with an ~ 80 fs pulse width (which is shorter than the period of excited CP oscillations), ~ 40 mW of average pump power, and a fluence of 22 $\mu\text{J}/\text{cm}^2$, the laser was tuned to the central wavelength of 850 nm (1.46 eV) to predominantly excite the E_{44} interband transitions of the SWNTs in the sample. A shaker-delay system

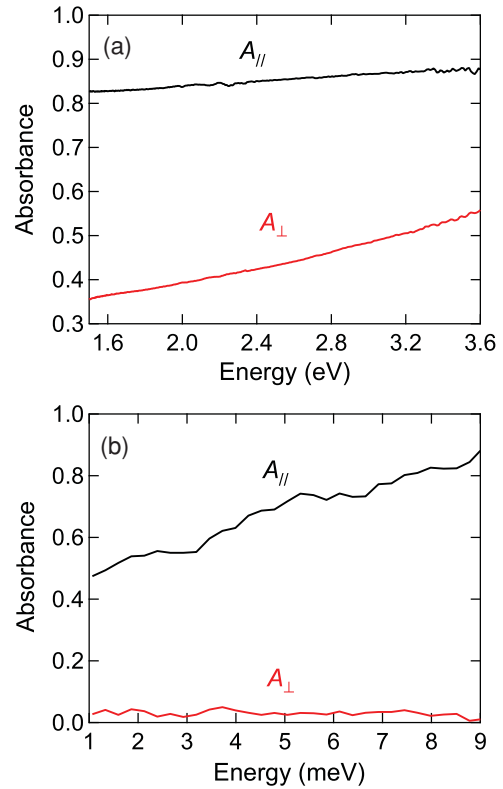


FIG. 1. (Color online) Absorption spectra of aligned single-walled carbon nanotubes in the (a) near-infrared to visible and (b) far-infrared (or terahertz) ranges for parallel ($A_{||}$) and perpendicular (A_{\perp}) polarization.

and balance detector was employed for fast-scan, real-time observation of CPs.

Figure 2 shows a typical pump-probe trace in the time-domain. To extract the CP oscillations, the large ($\Delta T/T < 10^{-2}$) electronic component needs to be subtracted by fitting a range in the time-domain, where differential transmission $\Delta T/T$ is plotted as a function of time t of the pump-probe trace with a number of exponentials that is then subtracted from the pump-probe trace. The resulting CP oscillations, with a signal on the order of $\sim 10^{-6}$, are shown in the inset of Fig. 2. Because our pump-probe measurements excite and probe mainly the E_{44} interband transitions of the SWNTs, the photo-created electron-hole pairs will undergo a very fast intraband relaxation to E_{11} ^{29,30} as well as a very fast exciton-exciton annihilation³¹⁻³⁷ at E_{11} from a high optical fluence. This is shown with the fast decay of the large electronic component of the pump-probe signal in Fig. 2. Therefore, as our measurements excite and probe E_{44} , our CP measurements are not affected by any saturation or exciton-exciton annihilation effects that can cause depolarization of the probe transmission.

As depicted in Fig. 3, two types of polarization-dependent pump-probe measurements were investigated. Type I configuration maintained the same polarization for the pump and probe, while the alignment axis of the sample was rotated. Type II configuration maintained the same orientation for the probe and sample, while the pump polarization was rotated. For Type II measurements, a half-waveplate provided 90-degree

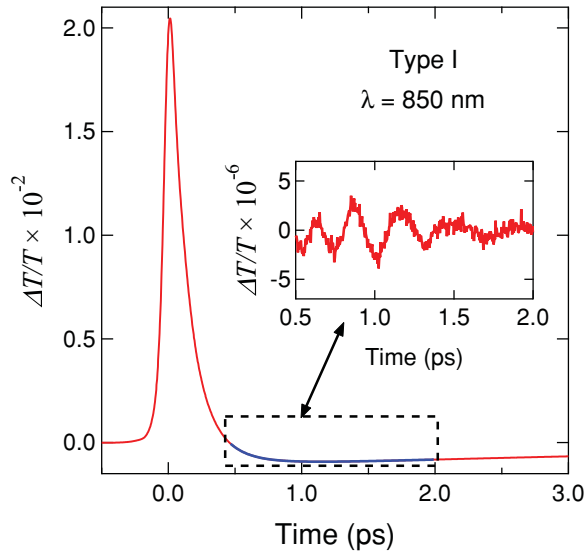


FIG. 2. (Color online) Typical differential transmission of the pump-probe signal for highly-aligned single-walled carbon nanotubes. The large electronic component is fit from $t = 0.5$ ps to $t = 2$ ps with a number of exponentials, which was then subtracted from the trace. The inset displays the extracted coherent phonon oscillations.

rotation of the pump. All measurements were performed at room temperature.

III. EXPERIMENTAL RESULTS

Results of our polarization-dependent ultrafast pump-probe differential transmission measurements on the aligned SWNT film for both Type I and Type II orientations are shown in Fig. 4. Here, it is seen that the typical differential transmission amplitude of the RBM CP oscillations is on the order of 10^{-6} , with a CP decay time of ~ 1.5 ps. This short decay time, compared to our earlier studies on individually suspended SWNTs in solution,^{18,23,25} is expected with our sample of bundled SWNTs.

Additionally, the overall amplitude of the CP oscillations can be affected by beating, as was demonstrated in our previous CP experimental work.¹⁸ Namely, the overall CP amplitude of a carbon nanotube ensemble can either increase or decrease with time when multiple phonon modes with similar frequencies are simultaneously excited, even though each excited mode is decaying exponentially with time. For example, in Fig. 4, it can be seen that the amplitude at $t = 0.5$ ps is smaller than the amplitude at $t = 1$ ps. This beating is expected during the entire lifetime of the envelope in the time-domain, but observation of this beating is limited to the signal-to-noise ratio of 10^{-6} .

As the polarization angle is rotated, we see a strong polarization anisotropy of the RBM CPs as a function of angle, where the strongest oscillations are observed at 0° while the signal is almost completely quenched at 90° for both Type I and Type II geometries.

Figure 5 shows CP spectra for different polarization angles for Type II configuration. To produce these spectra in the frequency domain, we calculated the Fourier transform (FT) of the time-domain CP oscillations. The frequencies of the

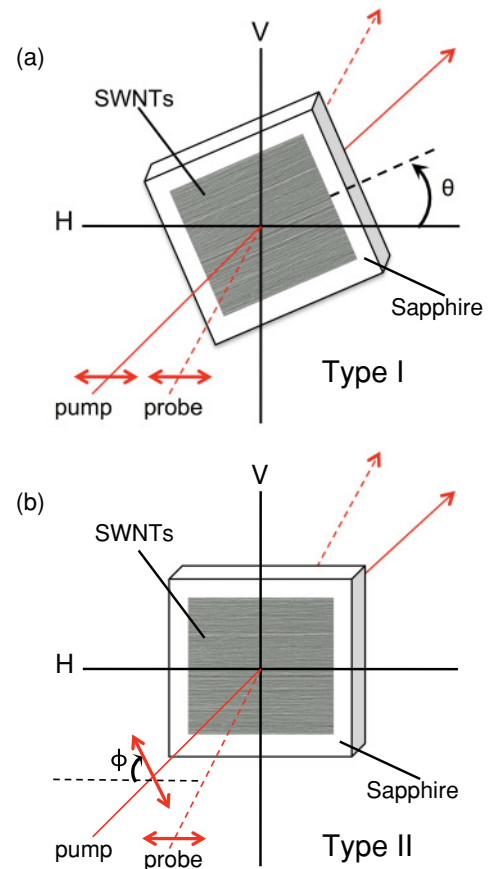


FIG. 3. (Color online) Scanning electron microscopy image of aligned single-walled carbon nanotubes, and the two experimental configurations employed in the current pump-probe spectroscopy work. (a) Type I: pump and probe polarizations are fixed and sample orientation is rotated. (b) Type II: probe and sample orientations are fixed and pump polarization is rotated.

CP oscillations have a wide range, from 50 to 200 cm^{-1} , and these frequencies agree with the calculated chiralities that have an optical transition energy of 1.46 eV from the Kataura plots.^{38,39} Although this transition energy corresponds to primarily E_{44} excitation, it is not limited to just E_{44} excitation and includes excitation of many other tubes with transition energy such as E_{33} , E_{55} , and E_{66} , which explains why we are exciting such a wide diameter distribution. As such, our measurements probe a large number of chiralities, many of which have overlapping RBM frequencies, and therefore our measurements with this SWNT sample can only determine a spectral range of frequencies, not a single chirality. The polarization anisotropy is clearly observed in the CP spectra. Figures 6(a) and 6(b) plot the integrated CP intensity of the FT for all excited nanotubes as a function of θ [in Fig. 6(a)] and ϕ [in Fig. 6(b)], where θ (ϕ) is the angle of rotation for the Type I (Type II) configuration.

IV. THEORY

We have developed a microscopic theory for the generation of coherent phonons in single-walled carbon nanotubes and their detection in coherent phonon spectroscopy experiments. Our microscopic theory is described in detail in Ref. 24, so

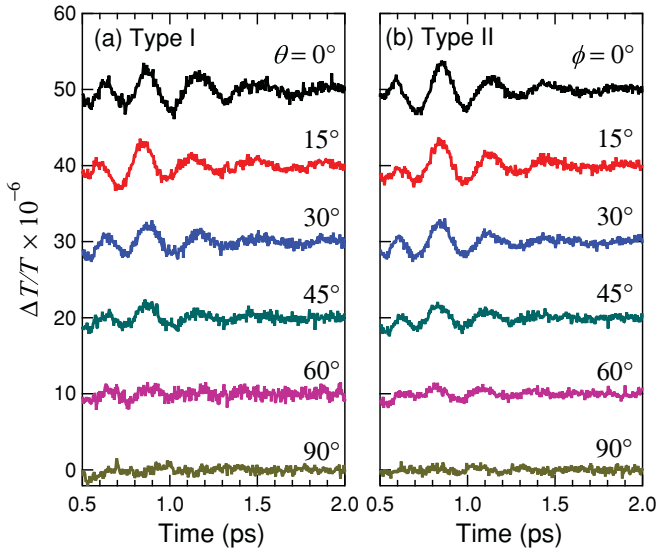


FIG. 4. (Color online) Experimental differential transmission data in the time domain showing coherent phonon oscillations of the radial breathing mode for different polarization angles in (a) Type I and (b) Type II configurations (see Fig. 3). The traces are vertically offset for clarity.

we only summarize the main points here and indicate how our earlier work has been extended to include polarization-dependent coherent phonon spectroscopy.

We treat the π and π^* electronic states in (n,m) carbon nanotubes using a third-nearest-neighbor extended tight binding (ETB) formalism developed by Porezag *et al.*⁴⁰ for carbon compounds. Using a density-functional-based parametrization, Porezag *et al.* derived analytic expressions for the Hamiltonian and overlap matrix elements that depend only on the C-C bond lengths. Using the ETB formalism, we obtain tight-binding wave functions and electronic energy

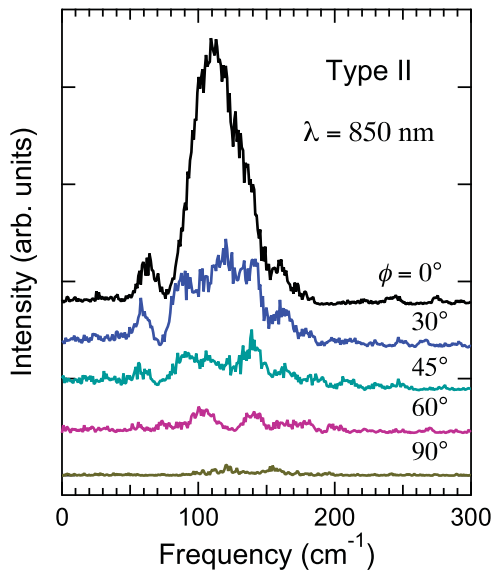


FIG. 5. (Color online) Coherent phonon spectra for different polarization angles in Type II configuration obtained through a Fourier transform of the time-domain data in Fig. 4(b). The traces are vertically offset for clarity.

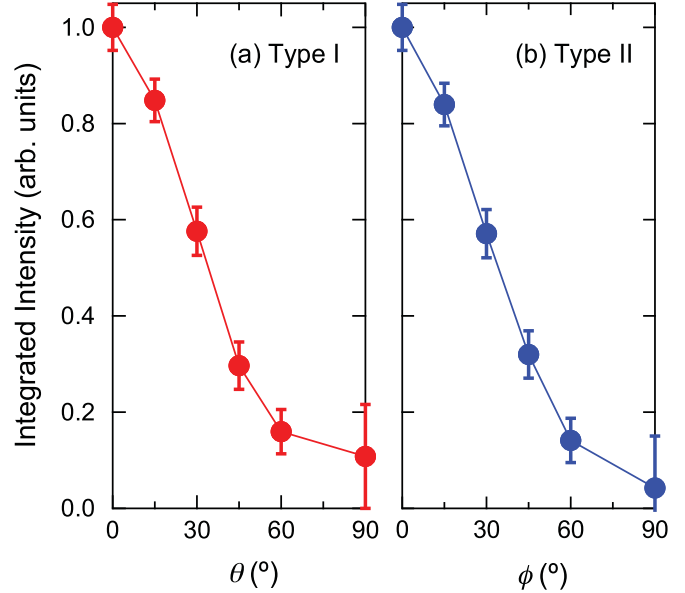


FIG. 6. (Color online) Spectrally integrated coherent phonon intensity as a function of angle, measured in (a) Type I and (b) Type II configurations.

levels $E_{s\mu}(k)$, where $s = c, v$ labels the conduction and valence bands, μ labels the cutting lines, and k is the 1D nanotube Brillouin zone.¹ By exploiting the screw symmetry of the nanotube, we can block-diagonalize the electronic Hamiltonian and overlap matrices into 2×2 blocks, one for each cutting line, as described in Appendix A of Ref. 24.

We treat nanotube lattice dynamics using a seven-parameter valence-force-field model described in Appendix B of Ref. 24. Exploiting the nanotube screw symmetry, the dynamical matrix can be block-diagonalized into 6×6 blocks, one for each cutting line, which can be solved for the phonon displacement vectors and dispersion relations $\omega_{p\nu}^2(q)$. In the dispersion relations, $\beta = 1, \dots, 6$ labels the phonon modes, ν is an angular momentum quantum number, and q is the phonon wave vector in the 1D nanotube Brillouin zone. Following the work of Jiang *et al.*⁴¹ and Lobo and Martins,⁴² we include four types of force field potentials; namely, the bond stretching, in-plane bond bending, out-of-plane bond bending, and bond twisting potentials. Our force-field potential energies are invariant under rigid rotations and translations (force constant sum rule), and, as a result, our phonon model correctly predicts the dispersion relation for the long-wavelength flexure modes.²⁴

The electron-phonon interaction is treated in a second-quantized formalism where the electron-phonon interaction matrix elements are evaluated in Appendix C of Ref. 24. In calculating electron-phonon matrix elements, we use $2p_z$ graphene atomic wave functions and screened atomic potentials obtained from an *ab initio* calculation.⁴¹

We obtain equations of motion for CP amplitudes using the Heisenberg equations as described by Kuznetsov and Stanton.⁴³ We assume that the optical pulse and photoexcited carrier distributions are distributed uniformly over the nanotube. In this case, only the $\nu = q = 0$ phonon modes are excited. To excite RBM CPs, the laser pulse must be short in comparison with the RBM phonon oscillation period.

For RBM CPs, the CP amplitude is proportional to the tube diameter $D(t)$. The tube diameter, being proportional to the CP amplitude, satisfies a driven oscillator equation

$$\frac{\partial^2 D(t)}{\partial t^2} + \omega^2 D(t) = S(t), \quad (1)$$

where ω is the angular frequency of the $\nu = q = 0$ RBM phonon mode. The driving function $S(t)$ for RBM coherent phonons is given by

$$S(t) \propto - \sum_{s\mu k} M_{s\mu}(k) [f_{s\mu}(k, t) - f_{s\mu}^0(k)], \quad (2)$$

where $M_{s\mu}(k)$ is the driving function kernel for RBM coherent phonons defined in Eq. (12) of Ref. 24 and $f_{s\mu}(k, t)$ and $f_{s\mu}^0(k)$ are the time-dependent and initial equilibrium carrier distribution functions, respectively.

From Eq. (2) we see that the driving function depends on the photoexcited carrier distribution functions. We treat photoexcitation of carriers in a Boltzmann equation formalism and obtain the photogeneration rate using Fermi's golden rule. In Ref. 24 we only considered linearly polarized laser pulses with the electric polarization vector parallel to the nanotube axis. For parallel polarization, optical transitions only occur between states with the same cutting line index μ , and the resulting photogeneration rate is given by Eq. (13) in Ref. 24.

In the present work, we consider linearly polarized pump and probe beams in which the electric polarization vector makes a finite angle with the nanotube axis. If $\hat{\epsilon}$ is the unit electric polarization vector for the pump, then the photogeneration rate is now given by

$$\begin{aligned} \left. \frac{\partial f_{s\mu}(k)}{\partial t} \right|_{\text{gen}} &= \frac{8\pi^2 e^2 u(t)}{\hbar n_g^2 (\hbar\omega)^2} \left(\frac{\hbar^2}{m_0} \right) \sum_{s'\mu'} |\hat{\epsilon} \cdot \vec{P}_{ss'}^{\mu\mu'}(k)|^2 \\ &\times (f_{s'\mu'}(k, t) - f_{s\mu}(k, t)) \delta(\Delta E_{ss'}^{\mu\mu'}(k) - \hbar\omega), \end{aligned} \quad (3)$$

where $\Delta E_{ss'}^{\mu\mu'}(k) = |E_{s\mu}(k) - E_{s'\mu'}(k)|$ are the k -dependent transition energies, $\hbar\omega$ is the pump photon energy, $u(t)$ is the time-dependent energy density of the pump pulse, e is the electronic charge, m_0 is the free electron mass, and n_g is the index of refraction in the surrounding medium. To account for spectral broadening of the laser pulses, the delta function in Eq. (3) was replaced with a Lorentzian line shape⁴⁴

$$\delta(\Delta E - \hbar\omega) \rightarrow \frac{\Gamma_p/(2\pi)}{(\Delta E - \hbar\omega)^2 + (\Gamma_p/2)^2}. \quad (4)$$

In Eq. (3), $\vec{P}_{ss'}^{\mu\mu'}(k)$ are the dipole-allowed optical matrix elements between the initial and final states, where μ and μ' are initial and final state cutting lines. For polarization parallel to the tube axis (taken to be \hat{z}), $\mu' = \mu$ and $\hat{z} \cdot \vec{P}_{ss'}^{\mu\mu'}(k) = P_{ss'}^{\mu\mu}(k)$ with the right-hand side being defined in Eq. (14) of Ref. 24. For linear polarization parallel to the x axis, $\mu' = \mu \pm 1$ and, in the notation of Ref. 24, we have

$$\begin{aligned} \hat{x} \cdot \vec{P}_{ss'}^{\mu, \mu \pm 1}(k) &= \frac{\hbar}{\sqrt{2}m_0} \frac{1}{2} \sum_{r'} C_{r'}^*(s', \mu \pm 1, k) \sum_{r\mathbf{J}} C_r(s, \mu, k) e^{i\phi_{\mathbf{J}}(k, \mu)} \\ &\times [M_x(r', r\mathbf{J}) \pm iM_y(r', r\mathbf{J})]. \end{aligned} \quad (5)$$

Similarly, for linear polarization along the y axis, we have

$$\hat{y} \cdot \vec{P}_{ss'}^{\mu, \mu \pm 1}(k) = \mp i[\hat{x} \cdot \vec{P}_{ss'}^{\mu, \mu \pm 1}(k)]. \quad (6)$$

In Eqs. (5) and (6), the atomic dipole matrix element vectors (which can be evaluated analytically) are given by

$$\mathbf{M}(r', r\mathbf{J}) = \int d\mathbf{r} \varphi_{r'\mathbf{0}}^*(\mathbf{r} - \mathbf{R}_{r'\mathbf{0}}) \nabla \varphi_{r\mathbf{J}}(\mathbf{r} - \mathbf{R}_{r\mathbf{J}}), \quad (7)$$

where the $2p_z$ orbitals $\varphi_{r\mathbf{J}}$ are defined in Eq. (C3) of Ref. 24.

In our experiments, a probe pulse is used to measure the time-varying absorption coefficient. In our theory, the time-varying optical properties measured by the probe pulse are obtained from the imaginary part of the dielectric function. For a linearly polarized probe pulse, we have

$$\begin{aligned} \varepsilon_2(\hbar\omega, t) &= \frac{8\pi^2 e^2}{A_t(\hbar\omega)^2} \left(\frac{\hbar^2}{m_0} \right) \sum_{ss'\mu\mu'} \int \frac{dk}{\pi} |\hat{\epsilon} \cdot \vec{P}_{ss'}^{\mu\mu'}(k)|^2 \\ &\times (f_{s\mu}(k, t) - f_{s'\mu'}(k, t)) \delta(\Delta E_{ss'}^{\mu\mu'}(k) - \hbar\omega), \end{aligned} \quad (8)$$

where $A_t = \pi(d_t/2)^2$ is the cross-sectional area of the tube and d_t is the equilibrium nanotube diameter. The Dirac delta function is replaced by a broadened Lorentzian of the form shown in Eq. (4). The photon energy of the probe pulse photons is $\hbar\omega$, and $\hat{\epsilon}$ is the probe unit polarization vector. In our experiments, the photon energy $\hbar\omega$ is the same for both pump and probe, while the polarization vector $\hat{\epsilon}$ may be different for pump and probe. To obtain the computed CP spectrum, we take the power spectrum of the computed differential transmission signal after background subtraction using the Lomb periodogram algorithm described in Ref. 45.

V. COMPARISON OF THEORY AND EXPERIMENT

To compare experiment with theory, we performed simulations of polarization-dependent CP spectroscopy on a (38,0) zigzag nanotube. This is a mod-2 semiconducting tube with a diameter of 3.01 nm. Our sample contains an ensemble of nanotubes with diameters centered around 3 nm,²⁸ and we expect that (38,0) tubes will contribute strongly to the CP signal for the ensemble since (i) the (38,0) tube has a diameter in the center of the measured diameter distribution and (ii) mod-2 zigzag tubes tend to have very strong intrinsic CP signals.^{18,24,25}

Our theoretical results for the (38,0) nanotube are shown in Fig. 7. Our computed electronic π band structure for the (38,0) tube is shown in Fig. 7(a). The bands are doubly degenerate with two distinct cutting lines corresponding to each band. The π valence bands have negative energy, and the π^* conduction bands have positive energy. For z -polarized light, the allowed E_{44} and E_{77} transitions (selection rule $\Delta\mu = 0$) giving rise to the strongest CP signals are indicated by vertical arrows.

The absorption coefficient for (38,0) nanotubes as a function of linearly polarized photon energy is shown in Fig. 7(b) for polarization angles varying from 0° (parallel to tube) to 90° (perpendicular to tube).

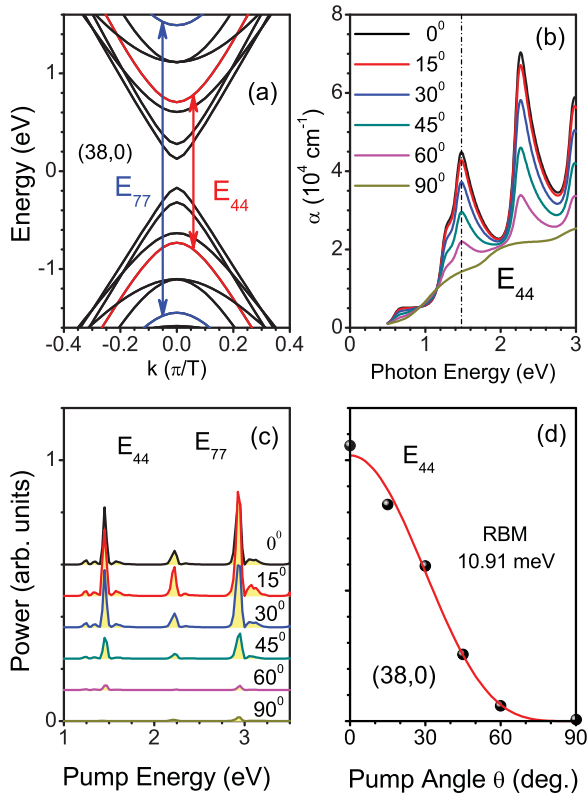


FIG. 7. (Color online) (a) Theoretical band structure for (38,0) nanotubes showing the strong E_{44} and E_{77} transitions for a polarization vector parallel to the tube. The wave vector k is expressed in units of π/T where $T = 4.31 \text{ \AA}$ is the length of the translational unit cell. (b) Computed absorption spectra for polarization angles varying from 0° (parallel to tube) to 90° (perpendicular to tube). (c) Coherent phonon spectra as a function of pump energy and pump polarization angle ϕ for RBM coherent phonons ($\omega = 10.91 \text{ meV}$). Coherent phonon spectra are Fourier transforms of computed time dependent differential transmission for Type II pump-probe experiments. (d) Integrated power (black dots) obtained by taking the area under the computed E_{44} peaks in lower left panel. We fit (red curve) the theoretical calculations to $A \cos^p(\phi)$ where A and $p = 4.017$ are fitting parameters.

For the (38,0) nanotube, the RBM phonons have a computed energy of 10.91 meV and an oscillation period of 379 fs . We simulate the generation of RBM CPs by pumping with a 50 fs pump pulse, which is much shorter than the RBM oscillation period. Polarization-dependent spectra for RBM CPs are shown in Fig. 7(c) for pump polarization angles ϕ ranging from 0° to 90° . In computing theoretical CP power spectra from computed differential reflectivity, we remove the initial transient during the pump phase. Background subtraction from the remaining signal is performed by fitting to a slowly varying cubic polynomial and subtracting this polynomial. Finally we remove a small residual dc signal by subtracting the overall time average. After this background subtraction is done, we take the Lomb periodogram to obtain the CP power spectra seen in Fig. 7(c). In these simulations, the probe polarization is kept fixed parallel to the tube axis (Type II geometry). As can be seen in the figure, the CP signal

is maximum when the pump is polarized parallel to the tube. As the pump photon energy is varied, we excite RBM CPs by successively photoexciting carriers in different bands. The strongest RBM CP signals are obtained by pumping at the E_{44} and E_{77} transitions. As the pump polarization angle increases, the RBM CP signal decreases until it is finally quenched when the pump polarization is perpendicular to the tube.

By taking the area under the RBM CP signal curves in the vicinity of the computed E_{44} transition energy near 1.48 eV , we obtain the integrated power as a function of pump polarization angle shown as black dots in Fig. 7(d). The integrated CP power can be well fit with a fitting function of the form $A \cos^p(\theta)$, where A and $p = 4.017$ are fitting parameters. The functional form of the fitting function $A \cos^p(\theta)$ was chosen since, in a simple effective mass picture, the squared optical matrix element near the band edge is proportional to $\cos^2(\theta)$, as pointed out in Ref. 3.

The polarization dependence of the RBM CP integrated power in Fig. 7(d) can be understood by examining Fig. 8. In Fig. 8(b) we plot the coherent RBM diameter oscillations as a function of the pump polarization angle θ . Fitting the theoretical results to $A \cos^p(\theta)$, we obtain $p = 2.15$ as indicated in the figure. For the RBM diameter oscillations we get $p \sim 2$, which can be understood as follows: The driving function $S(t)$ is proportional to the photogenerated carrier density, as seen in Eq. (2), and this in turn is proportional to the squared optical matrix element that has a $\cos^2(\theta)$ angular dependence.³ In Fig. 8(a) we plot the amplitude of the time-dependent differential transmission oscillations

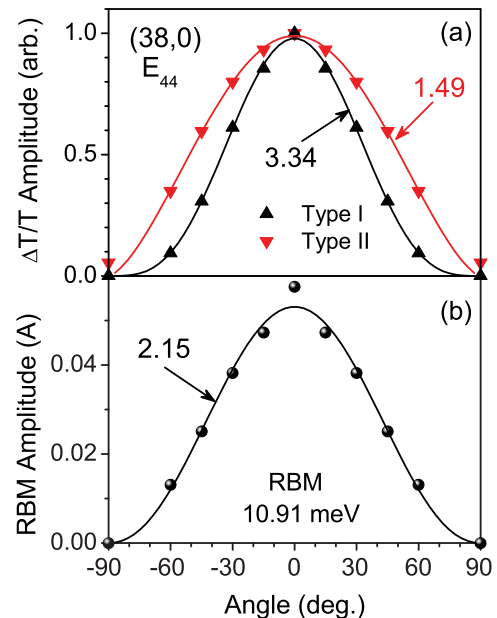


FIG. 8. (Color online) In (b) we plot the amplitude of RBM coherent phonon oscillations as a function of the pump polarization angle (θ or ϕ) for a (38,0) nanotube photoexcited by a 50 fs pump at the theoretical E_{44} transition. In (a) we plot the amplitude of the resulting differential transmission signal for Type I and II experiments as a function of angles θ and ϕ respectively. Our results are fit to $A \cos^p(\theta)$ [$A \cos^p(\phi)$] where numerical values of the best fit p are indicated in the figure.

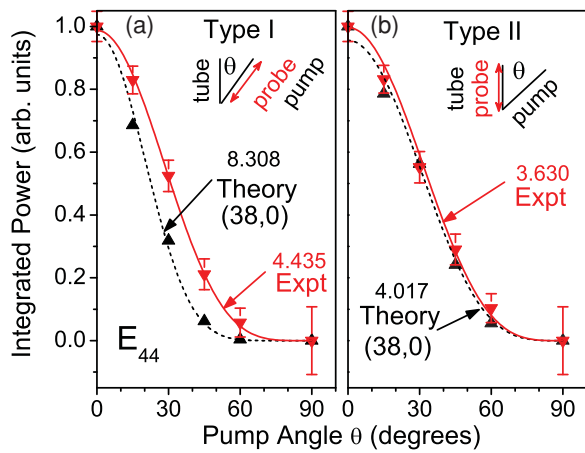


FIG. 9. (Color online) Integrated RBM coherent phonon power as a function of (a) θ for Type I and (b) ϕ for Type II experiments pumping close to the E_{44} transition. Experimental data points are red downward-pointing triangles fit by a solid red line. Theoretical data points for a (38,0) nanotube are black upward-pointing triangles and are fit by a black dashed line. The fitting functions are of the form $A \cos^p(\theta)$ and $A \cos^p(\phi)$ where the numerical values of the best fit p are indicated in the figure. The experimental curves have undergone background subtraction to obtain complete quenching at an angle of 90° and then have been rescaled so that the integrated power at an angle of 0° is equal to unity.

measured by the probe beam after background subtraction. For the differential transmission signal, we get $p \sim 2$ for Type II and double this amount for Type I. This can be understood in a crude way as follows. In Type II experiments the probe polarization is parallel to the tube axis and the pump polarization angle θ is varied. In this case, if we neglect optical matrix element k dependence, the signal should be roughly proportional to the amplitude of the diameter oscillations. In Type I experiments, on the other hand, the pump and probe polarizations are parallel and we should get an extra factor of $\cos^2(\phi)$ to account for anisotropy of the probe beam absorption. In our CP spectroscopy measurements, we extract the power spectrum of the differential transmission oscillations. The CP power spectrum should be proportional to the square of the amplitude of the differential transmission signal, which we anticipate will give us a $\cos^4(\phi)$ polarization dependence for Type II CP spectroscopy experiments and a $\cos^8(\theta)$ dependence for Type I CP spectroscopy experiments.

The experimental integrated CP power is obtained by taking the Fourier transform power spectrum of the time-dependent differential transmission data shown in Fig. 4 and then computing the area under the E_{44} peak in the resulting spectrum. The results for our Type I and Type II experiments are shown in Fig. 9, where the experimental data points are plotted as downward-pointing red triangles and the corresponding theoretical predictions are shown as upward-pointing black triangles. In overlaying the experimental and theoretical data points, we subtracted a background from the experimental data to obtain complete quenching at 90° . We then rescaled experimental and theoretical data (both in arbitrary units) so that the integrated power at 0° is equal to unity. We then fit experimental and theoretical data to functions of the

form $A \cos^p(\theta)$ [$A \cos^p(\phi)$]. The best fit functions for our experimental and theoretical results are shown in Fig. 9 as solid red and dashed black lines, respectively.

For the Type II experiments, where the probe polarization is fixed parallel to the average tube orientation, we get decent agreement between theory and experiment with best fit parameters $p = 4.017$ for theory and $p = 3.630$ for experiment. For the Type I experiments, where pump and probe polarization vectors are parallel to each other, there is a discrepancy between theory and experiment. As can be seen in Fig. 9(a), the best fit parameters are $p = 8.308$ for theory and $p = 4.435$ for experiment. The experimental fits in Fig. 9 would imply that the CP intensity scales roughly as $\cos^4(\theta)$ independently of the probe polarization. This seems unlikely given the anisotropy of the absorption coefficient in carbon nanotubes. In fact, from our theory, we would expect $p \sim 4$ for Type II and $p \sim 8$ for Type I.

We believe that the cause of this discrepancy is most likely due to misalignment effects. Our sample consists of an ensemble of nanotubes lying horizontally on a sapphire substrate. While the tubes are highly aligned, they are not perfectly aligned. To consider the effects of misalignment on the experimentally measured integrated CP intensity in a Type I experiment, we assume that the tube alignment angles on the transferred film are described by a Gaussian distribution function with a small standard deviation $\Delta\theta$. If the angle between the pump polarization vector and the ensemble averaged tube axis is θ , then the angles ϑ between the pump polarization vector and the axes of each tube in the ensemble are described by a Gaussian distribution

$$P(\vartheta, \theta, \Delta\theta) = \frac{1}{\sqrt{2\pi}(\Delta\theta)} \exp\left(-\frac{(\vartheta - \theta)^2}{2(\Delta\theta)^2}\right). \quad (9)$$

If the integrated RBM coherent phonon power for each nanotube in the ensemble is given by $A \cos^p(\vartheta)$, the ensemble averaged integrated power $I_{cp}(\theta, \Delta\theta)$ is obtained by taking the

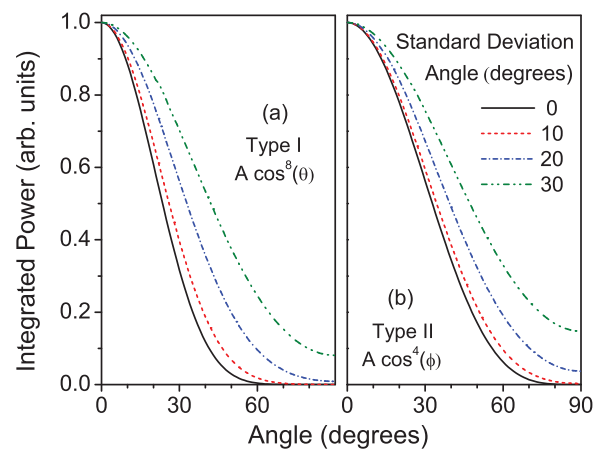


FIG. 10. (Color online) Effects of tube misalignment on integrated coherent phonon power for an ensemble of nanotubes with tube axis orientation angles following a Gaussian distribution. (a) Type I fitting function $A \cos^p(\theta)$ with $p = 8$ and (b) Type II fitting function $A \cos^p(\phi)$ with $p = 4$.

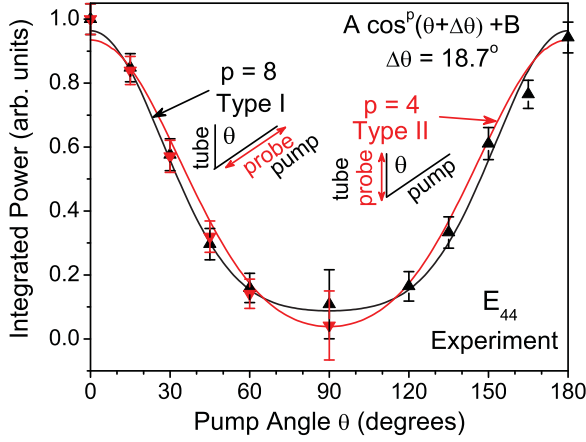


FIG. 11. (Color online) Experimental integrated RBM coherent phonon power for the E_{44} transition as a function of θ for Type I (black upward-pointing triangles) and ϕ for Type II (red downward-pointing triangles) experiments. Type I experiments are fit to $A \cos^p(\theta + \Delta\theta) + B$ where $p = 8$ (black dashed line) and Type II experiments are fit to $A \cos^p(\phi + \Delta\phi) + B$ for $p = 4$ (solid red line). A and B are background subtraction and rescaling parameters and the standard deviations for the random tube axis misalignment $\Delta\theta$ and $\Delta\phi$ are restricted to be the same for both Type I and II.

ensemble average over ϑ :

$$I_{cp}(\theta, \Delta\theta) = A \int_{-\infty}^{\infty} d\vartheta P(\vartheta, \theta, \Delta\theta) \cos^p(\vartheta), \quad (10)$$

respectively.

In Eq. (10), we extended the integration limits on ϑ to infinity in the limit of small $\Delta\theta$. If p is a positive integer, $I_{cp}(\theta, \Delta\theta)$ can be found analytically. Otherwise, it can be evaluated numerically. In the case of Type II experiments, the ensemble averaged integrated power is obtained by replacing θ with ϕ in Eqs. (9) and (10).

The effects of nanotube misalignment on the integrated CP power fitting function for an ensemble of Gaussian misaligned tubes is illustrated in Fig. 10, assuming $p = 8$ for Type I and $p = 4$ for Type II experiments. As the standard deviations $\Delta\theta$ [$\Delta\phi$] increase, quenching of the CP intensity is reduced and $I_{cp}(\theta, \Delta\theta)$ [$I_{cp}(\phi, \Delta\phi)$] become flatter.

Using this model, we are able to get reasonable fits to the experimentally measured CP intensity in both Type I and Type II experiments. We assume a fitting function of the form $A \cos^p(\theta + \Delta\theta) + B$ [$A \cos^p(\phi + \Delta\phi) + B$], where A and B are background subtraction and rescaling parameters and $\Delta\theta$ [$\Delta\phi$] is a random Gaussian distributed misalignment angle (standard deviation $\Delta\theta$ [$\Delta\phi$]). In our fitting procedure, we set $p = 8$ for Type I and $p = 4$ for Type II and use the same standard deviation for the tube misalignment angles in fitting both Type I and II data. The results of our fitting procedure are shown in Fig. 11, where the best fits for Type I and Type II geometries are shown as dashed black and solid red lines, respectively. Our best fit standard deviation is $\Delta\theta = \Delta\phi = 18.7^\circ$, which implies that the tube alignment angles on the sapphire substrate are $0^\circ \pm 9.35^\circ$. For small $\Delta\theta$ (measured in radians) the nematic order parameter is $S = \exp[-2(\Delta\theta)^2] = 0.81$.

Although a value of $S = 0.81$ indicates a strongly aligned sample, it is not perfectly aligned ($S = 1$). This is unlike previous work in the THz regime with these highly-aligned samples, where the nematic order parameter was calculated to be exactly $S = 1$.¹⁷ It is clear that there is a wavelength dependence of the nematic order parameter, but we believe this can be explained qualitatively as follows: Any slight misalignment in the sample would go undetected in the THz regime, as the wavelength is much larger than our visible wavelengths that can detect the misalignments. This could explain the difference in calculated nematic order parameter between our CP measurements and previous THz measurements, but nonetheless, regardless of the calculated differences with wavelength, our calculated nematic order parameter is still quite large and we can confidently confirm the high degree of alignment of the sample with our CP measurements.

VI. CONCLUSION

In summary, we investigated the polarization anisotropy of coherent phonon dynamics in highly-aligned single-walled carbon nanotubes and measured RBM coherent phonons as a function of polarization angle for two different types of experimental geometries. We saw an almost complete quenching of the RBM for both geometries, and while our theoretical model predicted the trends for both geometries, we found that it was necessary to extend our results to include the effects of nanotube misalignment.

Comparing our results with theory, we performed simulations of polarization-dependent CP spectroscopy on a (38,0) zigzag nanotube and also found a decrease in CP signal as optical polarization varied from parallel to perpendicular to the nanotube axis. Using those simulated results, we theoretically determined a $\cos^8(\theta)$ polarization dependence for Type I CP spectroscopy experiments and a $\cos^4(\phi)$ polarization dependence for Type II CP spectroscopy experiments for completely aligned nanotubes. However, to get a better agreement with experiment, it was necessary to include misalignment effects to our fitting. Including these effects improved our fits to the experimental data and gave us an estimate of 0.81 for the nematic order parameter of our sample.

ACKNOWLEDGMENTS

This work was supported by the DOE-BES (Grant No. DE-FG02-06ER46308), the National Science Foundation under Grant No. DMR-0325474, No. OISE-0530220, and No. DMR-0706313, the Robert A. Welch foundation under Grant No. C-1509, and the Office of Naval Research (ONR) under Contract No. 00075094. This research was also made with Government support under and awarded by DoD, Air Force Office of Scientific Research, National Defense Science and Engineering Graduate (NDSEG), 32 CFR 168a. Y.-S. Lim and K.-J. Yee are supported by a Korea Science and Engineering Foundation (KOSEF) grant funded by the Korean Government (Most) (R01-2007-000-20651-0). We acknowledge useful discussions with Andrew Rinzler at the University of Florida, thank Yaqiong Xu at Vanderbilt University for creating the patterned wafers that we used to grow the samples.

*kono@rice.edu; [www.ece.rice.edu/~kono].

- ¹R. Saito, G. Dresselhaus, and M. S. Dresselhaus, *Physical Properties of Carbon Nanotubes* (World Scientific, Singapore, 2003).
- ²J.-C. Charlier, X. Blase, and S. Roche, *Rev. Mod. Phys.* **79**, 643 (2007).
- ³H. H. Gommans, J. W. Alldredge, H. Tashiro, J. Park, J. Magnuson, and A. G. Rinzler, *J. Appl. Phys.* **88**, 2509 (2000).
- ⁴G. S. Duesberg, I. Loa, M. Burghard, K. Syassen, and S. Roth, *Phys. Rev. Lett.* **85**, 5436 (2000).
- ⁵A. Jorio, G. Dresselhaus, M. S. Dresselhaus, M. Souza, M. S. S. Dantas, M. A. Pimenta, A. M. Rao, R. Saito, C. Liu, and H. M. Cheng, *Phys. Rev. Lett.* **85**, 2617 (2000).
- ⁶Z. M. Li, Z. K. Tang, H. J. Liu, N. Wang, C. T. Chan, R. Saito, S. Okada, G. F. Li, J. S. Chen, N. Nagasawa *et al.*, *Phys. Rev. Lett.* **87**, 127401 (2001).
- ⁷A. Hartschuh, H. N. Pedrosa, L. Novotny, and T. D. Krauss, *Science* **301**, 1354 (2003).
- ⁸M. F. Islam, D. E. Milkie, C. L. Kane, A. G. Yodh, and J. M. Kikkawa, *Phys. Rev. Lett.* **93**, 037404 (2004).
- ⁹H. Ajiki and T. Ando, *J. Phys. Soc. Jpn.* **62**, 2470 (1993).
- ¹⁰J. P. Lu, *Phys. Rev. Lett.* **74**, 1123 (1995).
- ¹¹M. A. L. Marques, M. d'Avezac, and F. Mauri, *Phys. Rev. B* **73**, 125433 (2006).
- ¹²S. Zaric, G. N. Ostojic, J. Kono, J. Shaver, V. C. Moore, R. H. Hauge, R. E. Smalley, and X. Wei, *Nano Lett.* **4**, 2219 (2004).
- ¹³S. Zaric, G. N. Ostojic, J. Kono, J. Shaver, V. C. Moore, M. S. Strano, R. H. Hauge, R. E. Smalley, and X. Wei, *Science* **304**, 1129 (2004).
- ¹⁴M. F. Islam, D. E. Milkie, O. N. Torrens, A. G. Yodh, and J. M. Kikkawa, *Phys. Rev. B* **71**, 201401 (2005).
- ¹⁵J. Shaver, A. N. G. Parra-Vasquez, S. Hansel, O. Portugall, C. H. Mielke, M. von Ortenberg, R. H. Hauge, M. Pasquali, and J. Kono, *ACS Nano* **3**, 131 (2009).
- ¹⁶T. A. Searles, Y. Imanaka, T. Takamasu, H. Ajiki, J. A. Fagan, E. K. Hobbie, and J. Kono, *Phys. Rev. Lett.* **105**, 017403 (2010).
- ¹⁷L. Ren, C. L. Pint, L. G. Booshehri, W. D. Rice, X. Wang, D. J. Hilton, K. Takeya, I. Kawayama, M. Tonouchi, R. H. Hauge *et al.*, *Nano Lett.* **9**, 2610 (2009).
- ¹⁸Y.-S. Lim, K.-J. Yee, J.-H. Kim, E. H. H aroz, J. Shaver, J. Kono, S. K. Doorn, R. H. Hauge, and R. E. Smalley, *Nano Lett.* **6**, 2696 (2006).
- ¹⁹D. Song, F. Wang, G. Dukovic, M. Zheng, E. D. Semke, L. E. Brus, and T. F. Heinz, *Phys. Rev. Lett.* **100**, 225503 (2008).
- ²⁰K. Kang, T. Ozel, D. G. Cahill, and M. Shim, *Nano Lett.* **8**, 4642 (2008).
- ²¹A. Gambetta, C. Manzoni, E. Menna, M. Meneghetti, G. Cerullo, G. Lanzani, S. Tretiak, A. Piryatinski, A. Saxena, R. L. Martin *et al.*, *Nature Phys.* **2**, 515 (2006).
- ²²K. Kato, K. Ishioka, M. Kitajima, J. Tang, R. Saito, and H. Petek, *Nano Lett.* **8**, 3102 (2008).
- ²³J.-H. Kim, J. Park, B. Y. Lee, D. Lee, K.-J. Yee, Y.-S. Lim, L. G. Booshehri, E. H. H aroz, J. Kono, and S.-H. Baik, *J. Appl. Phys.* **105**, 103506 (2009).
- ²⁴G. D. Sanders, C. J. Stanton, J.-H. Kim, K.-J. Yee, Y.-S. Lim, E. H. H aroz, L. G. Booshehri, J. Kono, and R. Saito, *Phys. Rev. B* **79**, 205434 (2009).
- ²⁵J.-H. Kim, K.-J. Han, N.-J. Kim, K.-J. Yee, Y.-S. Lim, G. D. Sanders, C. J. Stanton, L. G. Booshehri, E. H. H aroz, and J. Kono, *Phys. Rev. Lett.* **102**, 037402 (2009).
- ²⁶Y.-S. Lim, J.-G. Ahn, J.-H. Kim, K.-J. Yee, T. Joo, S.-H. Baik, E. H. H aroz, L. G. Booshehri, and J. Kono, *ACS Nano* **4**, 3222 (2010).
- ²⁷C. L. Pint, Y.-Q. Xu, M. Pasquali, and R. H. Hauge, *ACS Nano* **2**, 1871 (2008).
- ²⁸C. L. Pint, Y.-Q. Xu, S. Moghazy, T. Cherukuri, N. T. Alvarez, E. H. H aroz, S. Mahzooni, S. K. Doorn, J. Kono, M. Pasquali *et al.*, *ACS Nano* **4**, 1131 (2010).
- ²⁹G. N. Ostojic, S. Zaric, J. Kono, V. C. Moore, R. H. Hauge, and R. E. Smalley, *Phys. Rev. Lett.* **94**, 097401 (2005).
- ³⁰C. Manzoni, A. Gambetta, E. Menna, M. Meneghetti, G. Lanzani, and G. Cerullo, *Phys. Rev. Lett.* **94**, 207401 (2005).
- ³¹F. Wang, G. Dukovic, E. Knoesel, L. E. Brus, and T. F. Heinz, *Phys. Rev. B* **70**, 241403 (2004).
- ³²L. Valkunas, Y.-Z. Ma, and G. R. Fleming, *Phys. Rev. B* **73**, 115432 (2006).
- ³³A. Srivastava and J. Kono, *Phys. Rev. B* **79**, 205407 (2009).
- ³⁴Y. Murakami and J. Kono, *Phys. Rev. B* **80**, 035432 (2009).
- ³⁵Y. Murakami and J. Kono, *Phys. Rev. Lett.* **102**, 037401 (2009).
- ³⁶Y.-Z. Ma, L. Valkunas, S. L. Dexheimer, S. M. Bachilo, and G. R. Fleming, *Phys. Rev. Lett.* **94**, 157402 (2005).
- ³⁷Y.-Z. Ma, J. Stenger, J. Zimmermann, S. M. Bachilo, R. E. Smalley, R. B. Weisman, and G. R. Fleming, *J. Chem. Phys.* **120**, 3368 (2004).
- ³⁸H. Kataura, Y. Kumazawa, Y. Maniwa, I. Umezumi, S. Suzuki, Y. Ohtsuka, and Y. Achiba, *Synth. Met.* **103**, 2555 (1999).
- ³⁹R. Saito and H. Kataura, *Carbon Nanotubes: Synthesis, Structure, Properties, and Applications* (Springer, Berlin, 2001), pp. 213–246.
- ⁴⁰D. Porezag, T. Frauenheim, T. K ohler, G. Seifert, and R. Kaschner, *Phys. Rev. B* **51**, 12947 (1995).
- ⁴¹J.-W. Jiang, H. Tang, B.-S. Wang, and Z.-B. Su, *Phys. Rev. B* **73**, 235434 (2006).
- ⁴²C. Lobo and J. L. Martins, *Z. Phys. D* **39**, 159 (1997).
- ⁴³A. V. Kuznetsov and C. J. Stanton, *Phys. Rev. Lett.* **73**, 3243 (1994).
- ⁴⁴S. L. Chuang, *Physics of Optoelectronic Devices* (Wiley, New York, 1995).
- ⁴⁵W. H. Press, S. A. Teukolsky, W. T. Vetterling, and B. P. Flannery, *Numerical Recipes* (Cambridge University Press, New York, 1992).